

Anomalous Quantum Diffusion and Conductivity of Quasicrystals

Didier Mayou

LEPES-CNRS, 25 avenue des Martyrs BP166, 38042 Grenoble, France.

A phenomenological diffusion law $L(t) \propto t^\beta$, where $L(t)$ measures the spreading of a wave-packet in a time t , is assumed for perfect quasicrystals. We show that it affects their conductivity with striking differences compared to the case of periodic metals. In the absence of defects the dissipative part of conductivity is non zero even at low frequencies contrary to the case of crystals. Also if $\beta < 1/2$ the d.c. conductivity increases when disorder increases and the so-called Drude peak, characteristic of metals, is replaced by a dip. Experimental results are briefly discussed.

PACS numbers: 71.23. Ft, 78.20.-e, 72.15.-v

Since the pioneering work of Kohmoto et al [1] numerous studies of quasiperiodic Hamiltonians have given evidences that the associated eigenstates are multifractal and critical with an algebraic decrease of their envelop at large distances [2–4]. These states lead to a peculiar quantum diffusion which is neither ballistic as in crystals nor diffusive as in metallic disordered systems but follows at sufficiently large time a power law $L(t) \propto t^\beta$ where $L(t)$ measures the spreading of a wave-packet in a time t [5–7]. β depends on the energy of the wave-packet and on the Hamiltonian but is restricted to $0 \leq \beta \leq 1$. For realistic models, periodic approximants of quasicrystals [8–10] have narrow bands, in agreement with the tendency to localization. For some phases these computations have even confirmed a multifractal character of eigenstates [8]. Electronic transport has been studied through Bloch-Boltzmann type approximation assuming a peculiar bandstructure [9–11] and this provides interesting information. Yet this approach does not consider the anomalous diffusion.

This paper presents a formalism that allows to discuss, for the first time to our knowledge, how the a.c. conductivity is affected by the anomalous diffusion. For d.c. conductivity of quasiperiodic systems with some disorder, the role of anomalous diffusion has been considered by several authors [12–14]. Using the Einstein formula $\sigma = 2e^2 n(E_F) D(E_F)$ where $n(E_F)$ is the density of states at the Fermi energy per spin and $D(E_F)$ the diffusivity of states at the Fermi energy one expects that the zero frequency conductivity is :

$$\sigma_{DC}(\tau) \simeq 2e^2 n(E) A \tau^{2\beta-1} \quad (1)$$

where τ is the time beyond which the propagation becomes diffusive due to disorder. In this scheme the propagation on time scale $t > \tau$ is diffusive with $D(E_F) \simeq \frac{L^2(\tau)}{3\tau} \simeq A \tau^{2\beta-1}$. For $\beta < 1/2$ the conductivity increases with disorder as observed in some quasicrystalline alloys [15]. From a dimensional argument one expects that the frequency dependent conductivity $\sigma_{AC}(\omega) = B \sigma_{DC}(\tau = \frac{1}{\omega}) \propto \frac{1}{\omega^{2\beta-1}}$ at the lowest frequencies where B is some complex number with a modulus of order unity. The real part of B is related to energy dissipation by the sys-

tem. For crystals it is zero but the dimensional argument alone cannot give its value in quasicrystals.

In this paper we study the zero or low frequency conductivity of a quasiperiodic Hamiltonian of independent electrons with and without static disorder. It is shown first that a suitably defined average of the conductivity at frequency ω is related to a quantity $\tilde{\sigma}(\omega)$ which has the analytical properties of a conductivity and is directly related to quantum diffusion. The behaviour of $\tilde{\sigma}(\omega)$ with frequency or disorder is thus representative of that of the conductivity and is studied in detail. Assuming an anomalous diffusion law in the perfect quasicrystal we obtain an exact result for the conductivity $\tilde{\sigma}_{Pure}(\omega)$ of the quasiperiodic system without defects. Then we consider the role of static disorder and introduce a relaxation time approximation for the velocity auto-correlation function which physical meaning and limits are discussed. This approximation allows to derive a generalized Drude formula for $\tilde{\sigma}(\omega)$ that interpolates between the above $\sigma_{DC}(\tau)$ (1) and $\tilde{\sigma}_{Pure}(\omega)$ as a function of the parameter $\omega\tau$. This formula implies a drastic deviation of optical conductivity from the case of crystals. We comment shortly on the conductivity of several quasicrystalline phases.

Let us define several quantities and give some exact relations between these quantities. We define first $\langle f \rangle_E$, the average diagonal element of an operator f among states at energy E :

$$\langle f \rangle_E = \frac{Tr[\delta(E - \hat{H})f]}{Tr[\delta(E - \hat{H})]} \quad (2)$$

Tr means a trace of an operator and $\delta(E - \hat{H})$ projects on eigenstates of the Hamiltonian $\hat{H}$ at energy E . Next we define a measure $X^2(E, t)$ of the spreading of wave-packets at energy E along the x-direction :

$$X^2(E, t) = \langle (X(t) - X(0))^2 \rangle_E \quad (3)$$

where $X(t)$ is the position operator along the x-direction at time t in the Heisenberg representation. $X^2(E, t)$ is a real and pair function of time. We define

also the auto-correlation function $C(E, t - t')$ for the velocity $V_x(t) = \frac{dX(t)}{dt}$ between t and t' and which from (3) satisfies:

$$C(E, t - t') = \langle V_x(t)V_x(t') + V_x(t')V_x(t) \rangle_E \quad (4)$$

$$\frac{dX^2(E, t)}{dt} = \int_0^t dt' C(E, t') \quad (5)$$

$C(E, t)$ is a real and pair function of t . For pure quasicrystals the phenomenological diffusion law reads :

$$X_0^2(E, t) \simeq At^{2\beta} \quad (6)$$

$$C_0(E, t) = \frac{d^2 X_0^2(E, t)}{dt^2} \simeq A2\beta(2\beta - 1)t^{2\beta-2} \quad (7)$$

(7) is obtained from (5) and (6). In periodic approximants, the scaling law $X_0^2(E, t) \simeq At^{2\beta}$ will be valid only up to some maximum time t_2 beyond which the periodicity is effective. Then quantities deduced from the scaling law (see below) will be valid for time scales $\tau \leq t_2$ or frequencies scales $\omega \geq \frac{1}{t_2}$. The Guarneri inequality [16] implies a singular continuous density of states of a three dimensional quasicrystal for $\beta < 1/3$. Yet if we consider periodic approximants we can assume that the density of states is absolutely continuous even for $\beta < 1/3$ but with the above restriction on time and frequency scales. From its definition (4) $C(E, t = 0) = 2 \langle V_x^2 \rangle_E$ is finite which implies that the propagation is ballistic at the lowest times. Thus the anomalous diffusion law can be valid only at sufficiently large times $t > t_1$. It occurs only when the wave-packet has sufficient time to "feel" specific atomic arrangements [17,18] and longer range quasiperiodic order. This remark is important for the sum-rule satisfied by conductivity (15).

We introduce $F(E, \omega)$ that appears in the formula [19] for the component $\sigma_{x,x}(\mu, \omega)$ of the conductivity tensor and satisfies:

$$F(E, \omega) = \frac{2\pi\hbar e^2}{\Omega} \text{Tr}[\delta(E - \hat{H})V_x\delta(E + \hbar\omega - \hat{H})V_x] \quad (8)$$

$$S(E, \omega) = F(E, \omega) + F(E - \hbar\omega, \omega) \quad (9)$$

$$S(E, \omega) = e^2 n(E) \int_{-\infty}^{+\infty} \exp(i\omega t) C(E, t) dt \quad (10)$$

Ω is the volume of the system. Starting from (8), (10) is easily shown by using the Fourier expansion of $\delta(E - \hat{H})$ and the cyclic property of a trace [20]. If $F(E, \omega)$ depends weakly on the energy E at a given ω then $F(E, \omega) \simeq F(E - \hbar\omega, \omega) \simeq S(E, \omega)/2$ which gives

$F(E, \omega)$ in terms of the velocity correlation function. This relation is often valid in disordered systems at low frequency [21]. Yet in quasicrystals there are important variations of electronic structure on small energy scale (tenths or hundredth of electron Volt and possibly less [8,9]) and the above assumption could have a vanishingly small range of validity. Since we are interested in general trends we consider an average of the conductivity at frequency ω over a range of chemical potential values (we could also consider the conductivity at very high temperature $kT \gg \hbar\omega$). More precisely we define averages of functions $g(E)$ by a convolution with a positive function $P(x)$ such that $\int dx P(x) = 1$:

$$\langle g(E) \rangle_P = \int dx P(x) g(E - x) \quad (11)$$

One can choose for example $P(x) = \frac{1}{2W} \exp(-\frac{|x|}{W})$ where W is its width. From the Kubo-Greenwood formula [19] at $T = 0$:

$$\langle \text{Re} \sigma_{x,x}(\mu, \omega) \rangle_P = \int_{\mu - \hbar\omega}^{\mu} \frac{dE}{\hbar\omega} \langle F(E, \omega) \rangle_P \quad (12)$$

where Re means the real part. If $W \gg \hbar\omega$ $F(E, \omega)$ and $F(E - \hbar\omega, \omega)$ have nearly the same weight in $\langle F(E, \omega) \rangle_P$ (11). Then only their sum $S(E, \omega)$ is relevant and $F(E, \omega)$ can be replaced by $\frac{S(E, \omega)}{2}$ in (12). One can write :

$$\langle \text{Re} \sigma_{x,x}(\mu, \omega) \rangle_P \simeq \int_{\mu - \hbar\omega}^{\mu} \frac{dE}{\hbar\omega} \langle \text{Re} \tilde{\sigma}(E, \omega) \rangle_P \quad (13)$$

$$\tilde{\sigma}(\mu, \omega) = e^2 n(\mu) \int_0^{\infty} \exp(i\omega t) C(\mu, t) dt \quad (14)$$

since for ω real $S(E, \omega) = 2\text{Re} \tilde{\sigma}(E, \omega)$. The relative difference between the two members of (13) is bounded by a term of order $\frac{\hbar\omega}{W}$ for ω real [20]. $\tilde{\sigma}(\mu, \omega)$ has the dimension of a conductivity. It is an analytical function of ω in the upper half of the complex plane. For large ω $\tilde{\sigma}(\mu, \omega) \propto \frac{1}{\omega}$ and the Kramers-Krönig relations can be proved. Finally the usual sum rule is also valid :

$$\int_0^{\infty} \text{Re} \tilde{\sigma}(\mu, \omega) d\omega = \pi e^2 n(\mu) \frac{C(\mu, t=0)}{2} = \pi e^2 \frac{n}{2m^*} \quad (15)$$

where the last equality holds for free electron like systems with electron density n and effective mass m^* . From now on we focus on the properties of $\tilde{\sigma}(\mu, \omega)$ since (13) shows that its variation with frequency or with defects drives the variation of the average conductivity $\langle \sigma(\mu, \omega) \rangle_P$. Due to Kramers-Krönig relations we expect also that the

imaginary part of $\tilde{\sigma}(\mu, \omega)$ is representative of that of the averaged conductivity $\langle \sigma(\mu, \omega) \rangle_P$ as discussed in [20]. Using the velocity correlation (7) associated to the anomalous diffusion law (6) we deduce $\tilde{\sigma}_{Pure}(\mu, \omega)$:

$$\tilde{\sigma}_{Pure}(\mu, \omega) \simeq e^2 n(\mu) A \Gamma(2\beta + 1) \left(\frac{i}{\omega}\right)^{2\beta-1} \quad (16)$$

since the anomalous diffusion is valid only at $t > t_1$ the above formula is valid for $\omega \leq \frac{1}{t_1}$. $\Gamma(z)$ is the Gamma function and is of order one for $0 \leq \beta \leq 1$ [22].

The real part of this expression is strictly positive if $0 < \beta < 1$ since $Re(i^{2\beta-1}) = \cos(\frac{\pi}{2}(2\beta - 1))$. Thus there is dissipation even for a perfect quasiperiodic system. This is in contrast with the case of crystals ($\beta = 1$) for which the dissipation is zero. A natural interpretation is obtained by comparing the bandstructure of crystals and that of approximants of quasicrystals in the limit of infinite unit cell. In a crystal the number of bands is finite and when ω tends to zero there is no more possibility for vertical interband transition at energy $\hbar\omega$ between an occupied state and an empty one. Since the system cannot absorb energy the real part of the conductivity is zero. On the contrary the number of bands of approximants with large unit cells increases indefinitely with the size of the unit cell. In the limit of infinitely large unit cell interband transition are possible even at the smallest frequencies and the dissipative part of conductivity is non zero.

We consider now the effect of static disorder. For weak static disorder numerical studies [23] give evidences that the propagation is diffusive on time scale $t > \tau$. There could be exceptions [24] at very strong quasiperiodic potential for which the quantum diffusion stays anomalous even with static disorder. In this case the result (16) is still valid. Our aim is to find an interpolation formula from the low frequency regime $\omega\tau \ll 1$ (1) to the high frequency regime $\omega\tau \gg 1$ (16). Let us assume a relaxation time approximation for $C(E, t)$:

$$C(E, t) \simeq C_0(E, t) \exp\left(-\frac{|t|}{\tau}\right) \quad (17)$$

where $C_0(E, t)$ is the velocity correlation function of the system without disorder. The physical meaning is that due to disorder the electron is scattered in states with no or smaller velocity correlation leading to a damping of the velocity correlation function. Using (17) we see that in (5) $\frac{dX_0^2(E, t)}{dt}$ is constant, and the propagation is diffusive, for $t > \tau$. The approximation (17) could be generalized by replacing the exponential by an average of damped exponentials. It will be clear that due to the linearity of equations this does not change our qualitative conclusions.

Assuming (17), using $X_0^2(E, 0) = 0$ (see(3)), $\frac{dX_0^2(E, t)}{dt} = 0$ at $t = 0$ (see (5)) and defining $z = (\frac{1}{\tau} - i\omega)$, $\tilde{\sigma}(\mu, \omega)$ (14) is equivalent to :

$$\tilde{\sigma}(\mu, \omega) \simeq e^2 n(\mu) A z^2 \int_0^\infty dt X_0^2(E, t) \exp(-zt) \quad (18)$$

$$\tilde{\sigma}(\mu, \omega) \simeq e^2 n(\mu) A \Gamma(2\beta + 1) \left(\frac{\tau}{1 - i\omega\tau}\right)^{2\beta-1} \quad (19)$$

(18) expresses a direct relation between quantum diffusion and optical conductivity. (19) is obtained from (18) and (6). Since the diffusion law (6) is valid for $t > t_1$ (19) applies only for $\omega < \frac{1}{t_1}$ and $\tau > t_1$ and this generalized Drude formula does not satisfy the sum rule (15). The point is that it interpolates between (16) for $\omega\tau \gg 1$ and (1) for $\omega\tau \ll 1$ (up to a numerical factor of order one).

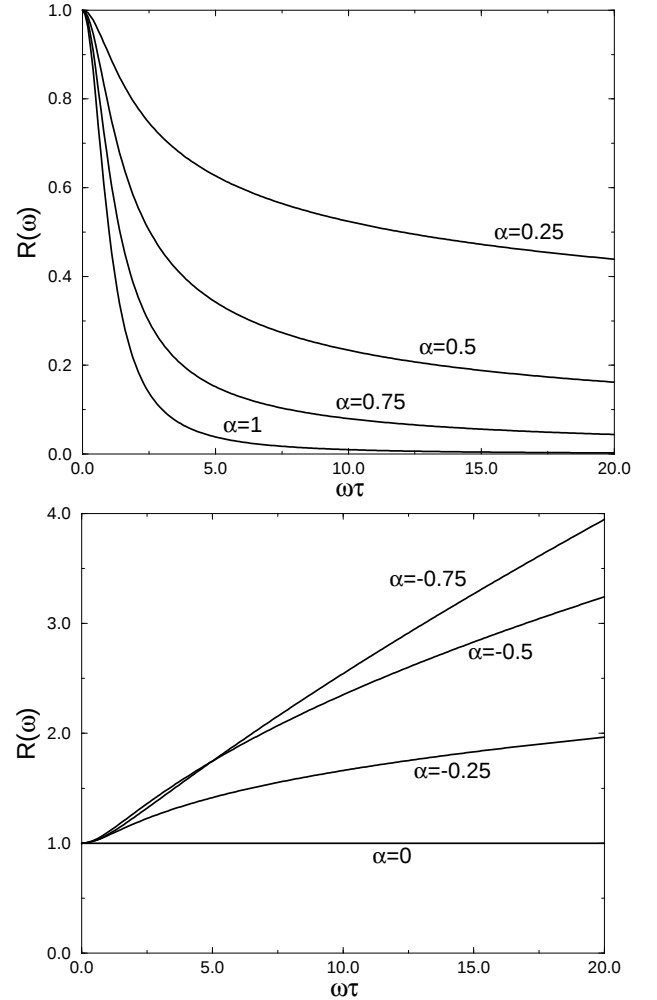


FIG. 1. Variation of $R(\omega) = \frac{Re\tilde{\sigma}(\mu, \omega)}{\tilde{\sigma}(\mu, 0)}$ as a function of $\omega\tau$ for several values of $\alpha = (2\beta - 1)$

Figure (1) shows $R(\omega) = \frac{Re\tilde{\sigma}(\mu, \omega)}{\tilde{\sigma}(\mu, 0)}$ as a function of $\omega\tau$. For $\alpha = 2\beta - 1 > 0$ the so-called Drude peak is less marked than in crystals yet the distinction may be difficult to establish experimentally. The deviation from

the case of crystals is drastic if $\alpha = 2\beta - 1 \leq 0$: instead of a Drude peak there is a plateau or a dip.

It is important to note that due to quantum interferences similar to those of disordered systems [12] the velocity correlation function should become negative on time scale $t > \tau$. This effect is beyond the relaxation time approximation (17) and becomes quantitatively important close to the metal-insulator transition [21]. According to the scaling theory of localization the parameter $g = \sigma_{Drude} X_0(\tau)$ must be compared to the universal critical conductance for three dimensional systems g_c . If $g \gg g_c$ the corrections are negligible and the relaxation time approximation is essentially correct. If g is comparable to g_c the relaxation time approximation is incorrect and if $g < g_c$ the quantum interferences even lead to an insulating state. Quantum interferences are effective on time scale $t > \tau$ or $\omega \leq \frac{1}{\tau}$ and it has been argued [12] that the system behave like a standard disordered system at these time scales. In any case one expects that (19) is correct for $\frac{1}{t_1} \geq \omega \geq \frac{1}{\tau}$. Even though the formalism is for static disorder, we believe that the generalized Drude formula (19) is better for an inelastic scattering since then quantum interferences cannot appear.

For many decagonal phases d-AlCuCo and icosahedral phases i-AlCuFe it seems that $\frac{\hbar}{\tau(T)} \simeq 310^{-2} eV$ for $T \leq 400K$ [15] then the full range in Figure (1) is $\hbar\omega \simeq 0.6eV$. A detailed comparison of the present theory with experiment is difficult since we consider only averages of the conductivity and also because quantum interferences effects [15] that are not included in the relaxation time approximation should play a role at low frequency ($\omega\tau(T) \leq 1$). Yet since i-AlCuFe [25] and i-AlPdRe [26] do not exhibit a Drude peak they are similar to the case $2\beta - 1$ negative. Correlatively (in agreement with (19)) the d.c. conductivity increases with temperature and probably also with the addition of defects. For d-AlCuCo [27], which consists of quasiperiodic planes stacked periodically in the z-direction, the dissipative part of conductivity along the quasiperiodic planes depends weakly on frequency which is consistent with $2\beta - 1$ close to zero. Correlatively the conductivity in the quasiperiodic planes depends weakly on temperature. Along the z direction the conductivity of d-AlCuCo is that of good metals.

To conclude let us recall that a suitably defined average of the conductivity can be related to the quantum diffusion in the system $X_0(\mu, t)$ as expressed by (13, 18). Striking differences with crystals occur when $X_0(\mu, t)$ deviates from a ballistic law and this seems to be in agreement with experimental results.

I would like to thank B.K. Chakraverty, F.Trioizon, T. Grenet, C. Berger and P. Lefebvre for discussions.

- [1] M.Kohmoto, L.P.Kadanoff and C.Tang, Phys. Rev. Lett. **50**, 1870 (1983)
- [2] S.Ostlund et al. Phys.Rev.Lett.**50**, 1873 (1983)
- [3] T.Rieth and M. Schreiber Phys.Rev.B**51**, 15827 (1995)
- [4] T. Fujiwara and H. Tsunetsugu in Quasicrystals : The state of the Art, edited by D.P. Di Vincenzo and P.J. Steinhardt (World Scientific, Singapore, 1991) p 343-360
- [5] F.Piéchon Phys. Rev. Lett. **76**, 4372 (1996). J. Vidal and R. Mosseri, Proceedings of ICQ7 (to be published Elsevier 2000)
- [6] B. Passaro, C. Sire and V.G. Benza Phys.Rev.B **46**, 13751 (1992)
- [7] I. Guarneri and G. Mantica, Phys. Rev. Lett. **73**, 3379 (1994)
- [8] T. Fujiwara, T. Mitsui and S. Yamamoto , Phys.Rev.B **53**, R2910 (1996)
- [9] T. Fujiwara, S. Yamamoto and G.Trambly de Laissardiére, Phys. Rev. Lett. **71**, 4166 (1993). S.Roche and T. Fujiwara, Phys.Rev.B **58**, 11338 (1998)
- [10] J. Hafner and M. Krajci Phys.Rev.Lett.**68**, 2321 (1992)
- [11] S.E.Burkov, T.Timusk and N.W. Ashcroft, J.Phys.C**4**, 9447 (1992)
- [12] E. Belin and D. Mayou Phys. Scr. T**49**, 356 (1993) D. Mayou in Lectures on Quasicrystals, Edited by F. Hippert and D. Gratias (Les Editions de Physique, Les Ulis 1994)
- [13] C. Sire, in Lectures on Quasicrystals, Edited by F. Hippert and D. Gratias (Les Editions de Physique, Les Ulis 1994)
- [14] J. Bellissard, A. van Elst and H. Schulz-Baldes J. Math. Phys.**35**, 5373 (1994) J. Bellissard Proceedings of ICQ7 (to be published Elsevier 2000)
- [15] C. Berger in Lectures on Quasicrystals, Edited by F. Hippert and D. Gratias (Les Editions de Physique, Les Ulis 1994)
- [16] I. Guarneri, Europhys.Lett. **21**, 729 (1993)
- [17] G. Trambly de Laissardiére and D. Mayou Phys.Rev. B **55**, 2890 (1997)
- [18] C. Janot, J.Phys.Condens.Matter **9**, 1493 (1997)
- [19] R. Kubo J.Phys.Soc.Jpn**12**, 570 (1957) D.A. Greenwood, Proc.Phys.Soc.London **71**, 585 (1958)
- [20] D. Mayou To be published
- [21] P.A. Lee and T.V. Ramakrishnan Rev. Mod. Phys. **57**, 287 (1985)
- [22] M. Abramowitz and I. A. Stegun, *Handbook of mathematical functions* (Dover, New York, 1970).
- [23] S. Roche and D. Mayou, Phys. Rev. Lett. **79**, 2518 (1997); S. Roche, G.Trambly de Laissardiére, D. Mayou, J. Math.Phys. **38**(4)1794 (1997)
- [24] F. Trioizon, D. Mayou Proceedings of ICQ7 (to be published Elsevier 2000).
- [25] C.C. Homes et al. Phys.Rev. Lett.**67**, 2694 (1991)
- [26] D.N. Basov et al. Phys.Rev. Lett.**73**, 1865 (1994) A.D. Bianchi et al. Phys.Rev.B. **55**, 5730 (1997) J. Delahaye, J.P. Brison and C. Berger Phys.Rev.Lett. **81**, 4204 (1998)
- [27] D.N. Basov et al. Phys.Rev. Lett.**72**, 1937 (1994)